

MOSO® Bamboo X-treme® Outdoor Decking

MOSO® Bamboo X-treme® Decking is a solid, Thermo-Density® board, made from compressed bamboo strips. A special, unique heat-treatment process at 200°C provides MOSO® Bamboo X-treme® with the highest durability class possible in the appropriate EU norms (see technical characteristics below) and the compression increases the hardness and stability. A unique feature of MOSO® Bamboo X-treme® is the end-match system: this can only be done with very stable materials and enables the connection of an unlimited number of boards lengthways. The special symmetrical shape of the sides allows the possibility to choose either the grooved or the flat surface, and allows for quick installation with MOSO® Fasteners. Like any tropical hardwood species, when exposed to outdoor conditions, MOSO® Bamboo X-treme® will turn grey over time creating a very natural look.

Standard Groove / Flat
(reversible)



Curved




V-Groove / Brushed
(reversible)



2 Non-slip lines



End-matched



*) Ends of the boards are protected with Sikkens Kodrin WV 456 sealer.

Oiled Woca*	Unfinished	Surface	Edge groove	End-matched	Length edges	End edges	Dimensions (mm)
BO-DTHT171G	BO-DTHT170G	Standard Groove/Flat	Yes	Yes	R3	2 mm x 45°	1850x137x20
BO-DTHT171G1	BO-DTHT170G1	Standard Groove/Flat	One side	Yes	R3	2 mm x 45°	1850x137x20
BO-DTHT181G		Standard Groove/Flat	Yes	Yes	R3	2 mm x 45°	1850x137x18
BO-DTHT171G-AS2		2 Non-slip lines	Yes	Yes	R3	2 mm x 45°	1850x137x20
BO-DTHT371	BO-DTHT370	Standard Groove/Flat	No	Yes	R3	2 mm x 45°	1850x137x30
BO-DTHT191G	BO-DTHT190G	Standard Groove/Flat	Yes	Yes	R3	2 mm x 45°	1850x155x20
BO-DTHT191G-C		Curved	Yes	Yes	R3	2 mm x 45°	1850x155x20
BO-DTHT191GV-R		V-Groove/Brushed	Yes	Yes	R3	2 mm x 45°	1850x155x20
BO-DTHT211G	BO-DTHT210G	Standard Groove/Flat	Yes	Yes	R3	2 mm x 45°	1850x178x20
BO-DTHT231GV-R		V-Groove/Brushed	Yes	Yes	R3	2 mm x 45°	1850x208x20
BO-DTHT163G-CHV		Chevron Flat	Yes	No	R3	2 mm x 45°	566(703)x137x20


installation summary

- Install suitable, fixed, stable and durable sub frame joists. MOSO recommends the use of MOSO® Bamboo X-treme® Sub frame joists.
- Determine which side of the board will be used: the grooved or flat surface.
- Fix the boards on the sub frame using fasteners (to be inserted in the grooves of the board) or alternatively with screws (through the surface).
- Use a 1-2% slope and ensure good ventilation. The slope is not necessary for the curved boards.
- After installation: make sure proper cleaning and maintenance is done, according to the chosen finish.
- When not applying outdoor oil regularly, the deck will acquire a grey colour tone and the typical bamboo wood grain structure will become less visible.
- Bamboo X-treme® is available pre-oiled or unfinished. In order to maintain the rich brown colour an exterior penetrating oil for hardwoods is recommended to be applied 3 to 4 months after installation. We advise to apply the initial coat 3-4 months after installation.
- For further info: please see the installation/maintenance instructions.
- Store in a cool and dry place away from direct sunlight, and protected from weather influences, dirt and dust.
- Full version available at ► www.moso-bamboo.com/x-treme/decking
- Installation instructions for chevron decking board available at ► www.moso-bamboo.com/x-treme/decking-chevron

technical characteristics and certifications

- Density: +/- 1150 kg/m³
- Dimensional stability: length: + 0.1 %; width + 0.9% (24 hours in water 20°C)
- Resistance to Indentation - Mean value Brinell Hardness: ≥ 9.5 kg/mm² (EN 15334)
- Reaction to fire: Class Bfl-s1 (EN 13501-1)
- Flame spread index: Class A (ASTM E84)
- Slip resistance - Pendulum friction test: PTV 55 (Standard Groove/Flat, Dry), PTV 29 (Standard Groove/Flat, Wet), PTV 91 (Brushed, Dry), PTV 42 (Brushed, Wet) (CEN/TS 16165 Annex C - CEN/TS 15676)
- Slip resistance - Shod ramp test: R 10 (Standard Groove/Flat), R 11 (Brushed), R 13 (Non-slip) (CEN/TS 16165 Annex B - DIN 51130)
- Slip resistance - Barefoot ramp test: Class C (Standard Groove/Flat) (CEN/TS 16165 Annex A - DIN 51097)
- Thermal emittance: 0.81 (ASTM C1371) ¹⁾
- Solar Reflectance (SR): 0.32 (ASTM C1549) ¹⁾
- Solar Reflectance Index (SRI): Low 27, Medium 30, High 33 (ASTM E1980) ¹⁾
- Modulus of Elasticity: 13565 N/mm² (mean value - EN 408)
- Bending strength: 54.4 N/mm² (characteristic value - EN 408)
- Biological durability: Class 1 (EN 350 / CEN/TS 15083-2), simulated graveyard test / Class 1 (EN 350 / CEN/TS 15083-1)
- Effectiveness against Blue Stain: Class 0 (EN 152)
- Use Class: Class 4 (EN 335)
- CO₂ neutral: LCA report TU Delft (ISO 14040/44) (www.moso-bamboo.com/lca)
- Environmental Product Declaration - EPD (EN 15804) (www.moso-bamboo.com/epd)
- FSC®: Products available with FSC® certification on request.
- Contribution LEED BD+C - v4: MR 1, MR 2, MR 3 (FSC®), EQ 2, SS 7 v2009: MR 6, MR 7 (FSC®), IEQ 4.3, IEQ 4.4
- Contribution BREEAM: MAT 1, MAT 3 (FSC®), MAT 5 (HD)
- Guarantee: 25 years

¹⁾ Tested on 3 years weathered MOSO® Bamboo X-treme®.

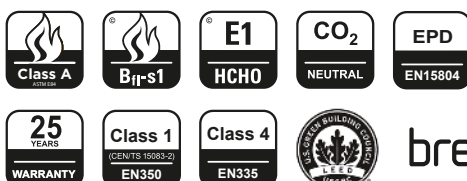

The mark of responsible forestry
FSC® C002063